



Resonant X-ray Ptychographic Tomography of P3HS Solar Cells

Jørgensen, Peter S.; Fevola, Giovanni; Ramos, Tiago; Rein, Christian; Small, Cephas ; Stingelin, Natalie ; Andreasen, Jens W.

Publication date:
2017

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):
Jørgensen, P. S., Fevola, G., Ramos, T., Rein, C., Small, C., Stingelin, N., & Andreasen, J. W. (2017). *Resonant X-ray Ptychographic Tomography of P3HS Solar Cells*. 1. Poster session presented at European XFEL Users' Meeting 2017, Hamburg, Germany.

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.


Resonant X-ray Ptychographic Tomography of P3HS Solar Cells

Peter S. Jørgensen^a, Giovanni Fevola^a, Tiago Ramos^a, Christian Rein^a, Cephas Small^b, Natalie Stingelin^b, Jens W. Andreasen^a


^a Technical University of Denmark, ^b Imperial College

Overview and motivation

Organic solar cells are a promising technology as a cost efficient alternative to silicon solar cells. Imaging of the internal structure is crucial for fundamental understanding of the internal processes and future developments. Of particular interest is the P3HT:PCBM layer which has proven challenging to image due to small differences in the refractive index of the two constituent materials. In this work we present preliminary results on attempting to increase the contrast in the layer by replacing S in P3HT with Se (P3HSe).

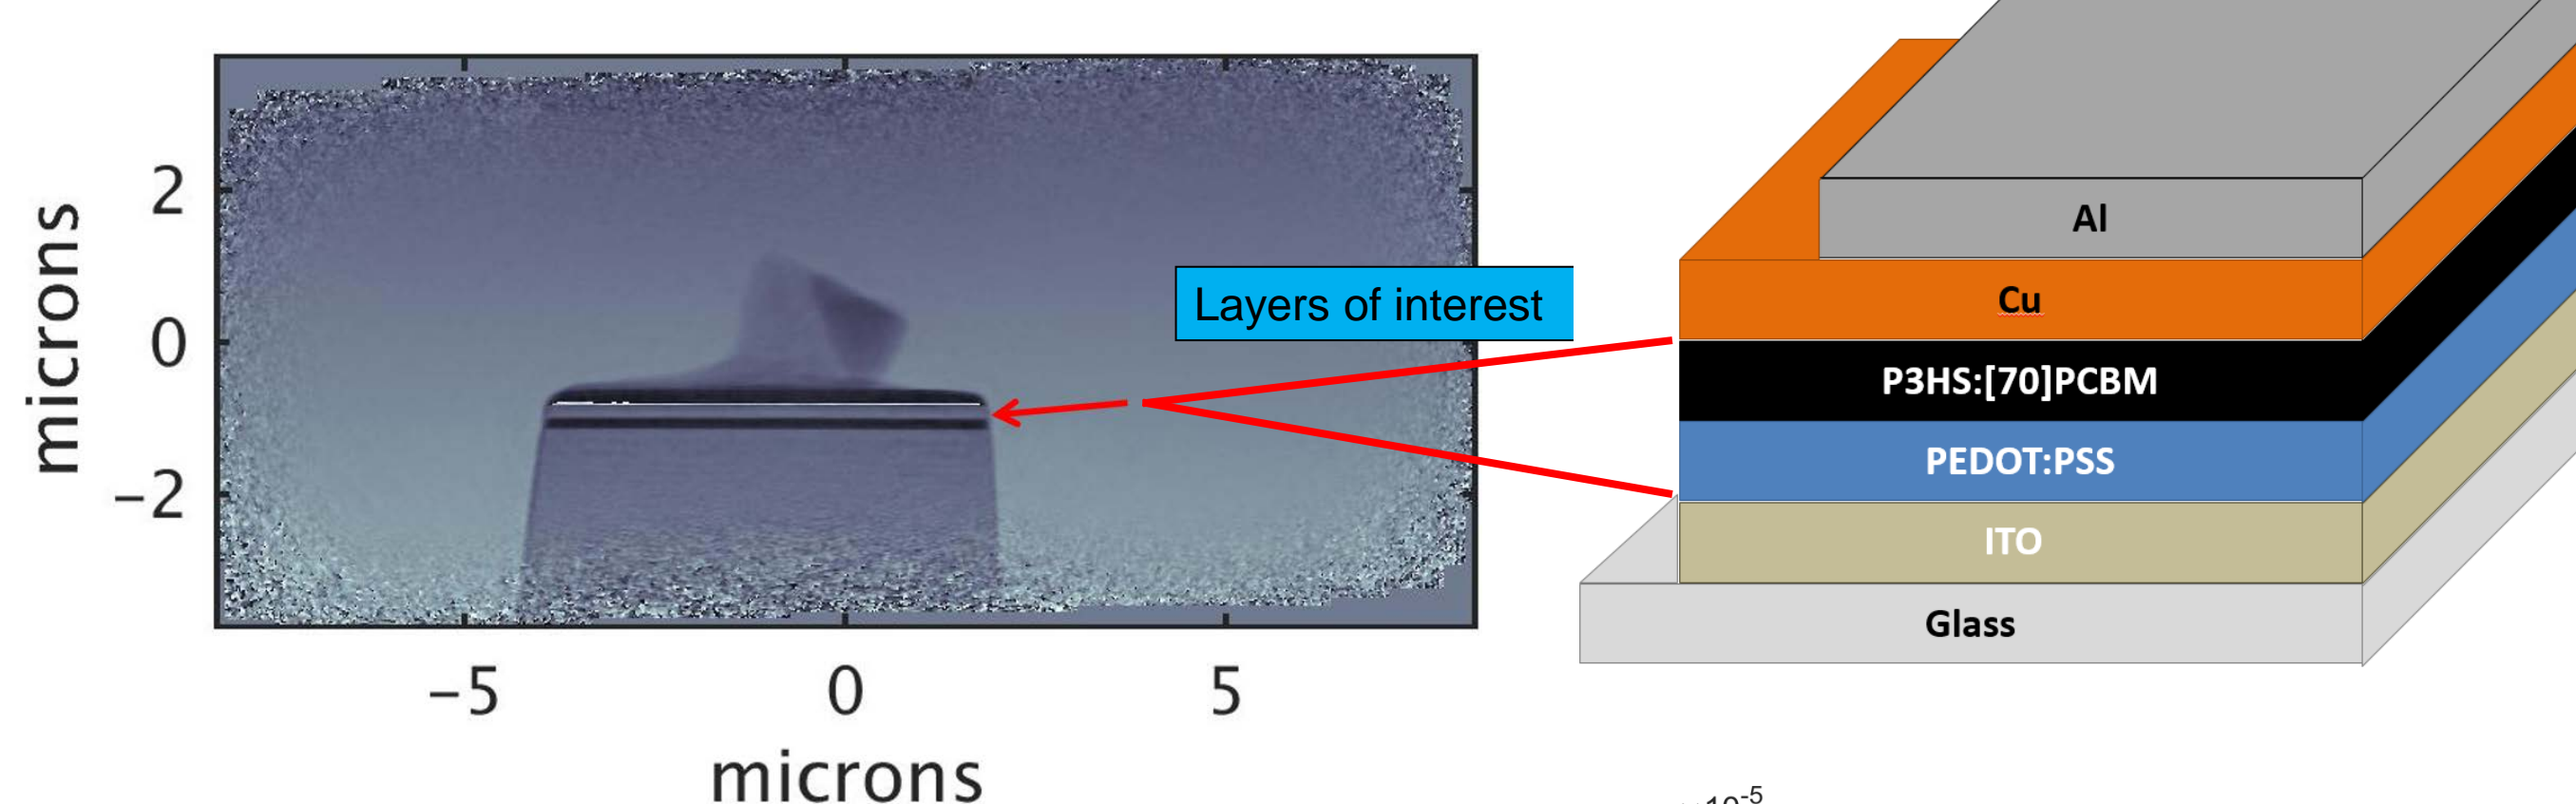


The same sample was imaged at three energies by ptychographic X-ray computed tomography. The energies were chosen as: the optimal energy for the beamline (6.2 keV), just below the Se K edge (12.51 keV) and at the Se K edge (12.66 keV) respectively. All the data was acquired at the cSAXS beamline at the Paul Scherrer Institute, Switzerland.

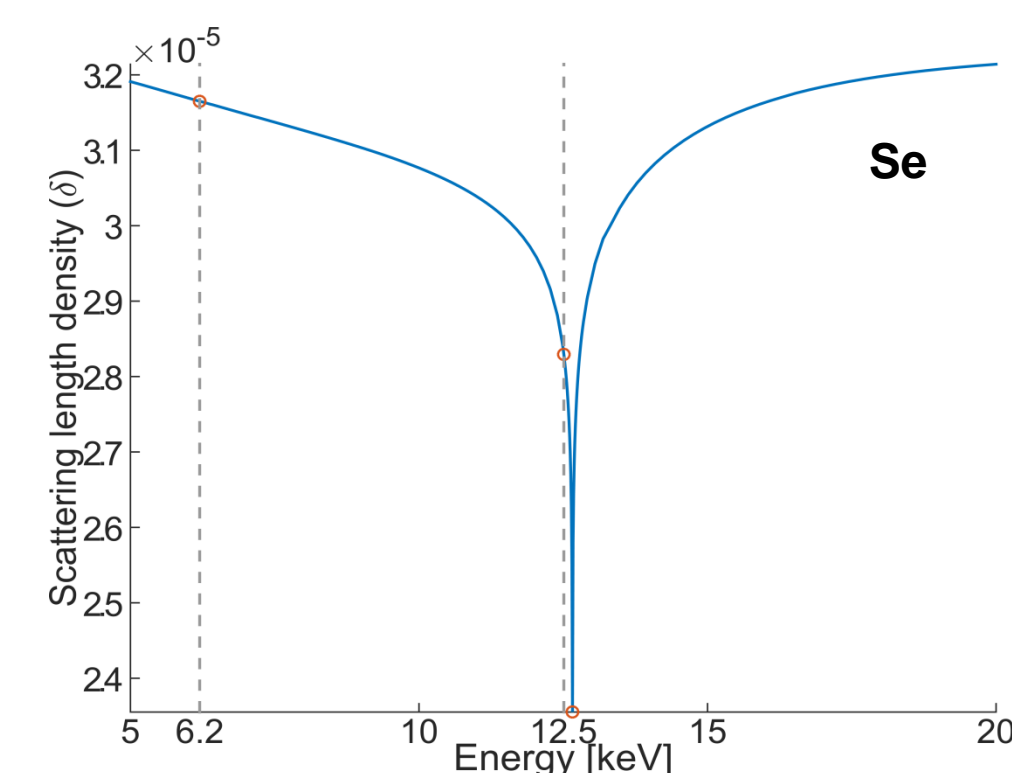


Individual voxel layers in the layer of interest

In the layer of interest a histogram was constructed for each layer of voxels. The images show the probability density of each histogram as a function of δ and the layer location (relative to the bottom of the layer of interest)

Layers were sampled parallel to the bottom layer transition to correct for the minor tilt of the sample relative to the voxel grid.

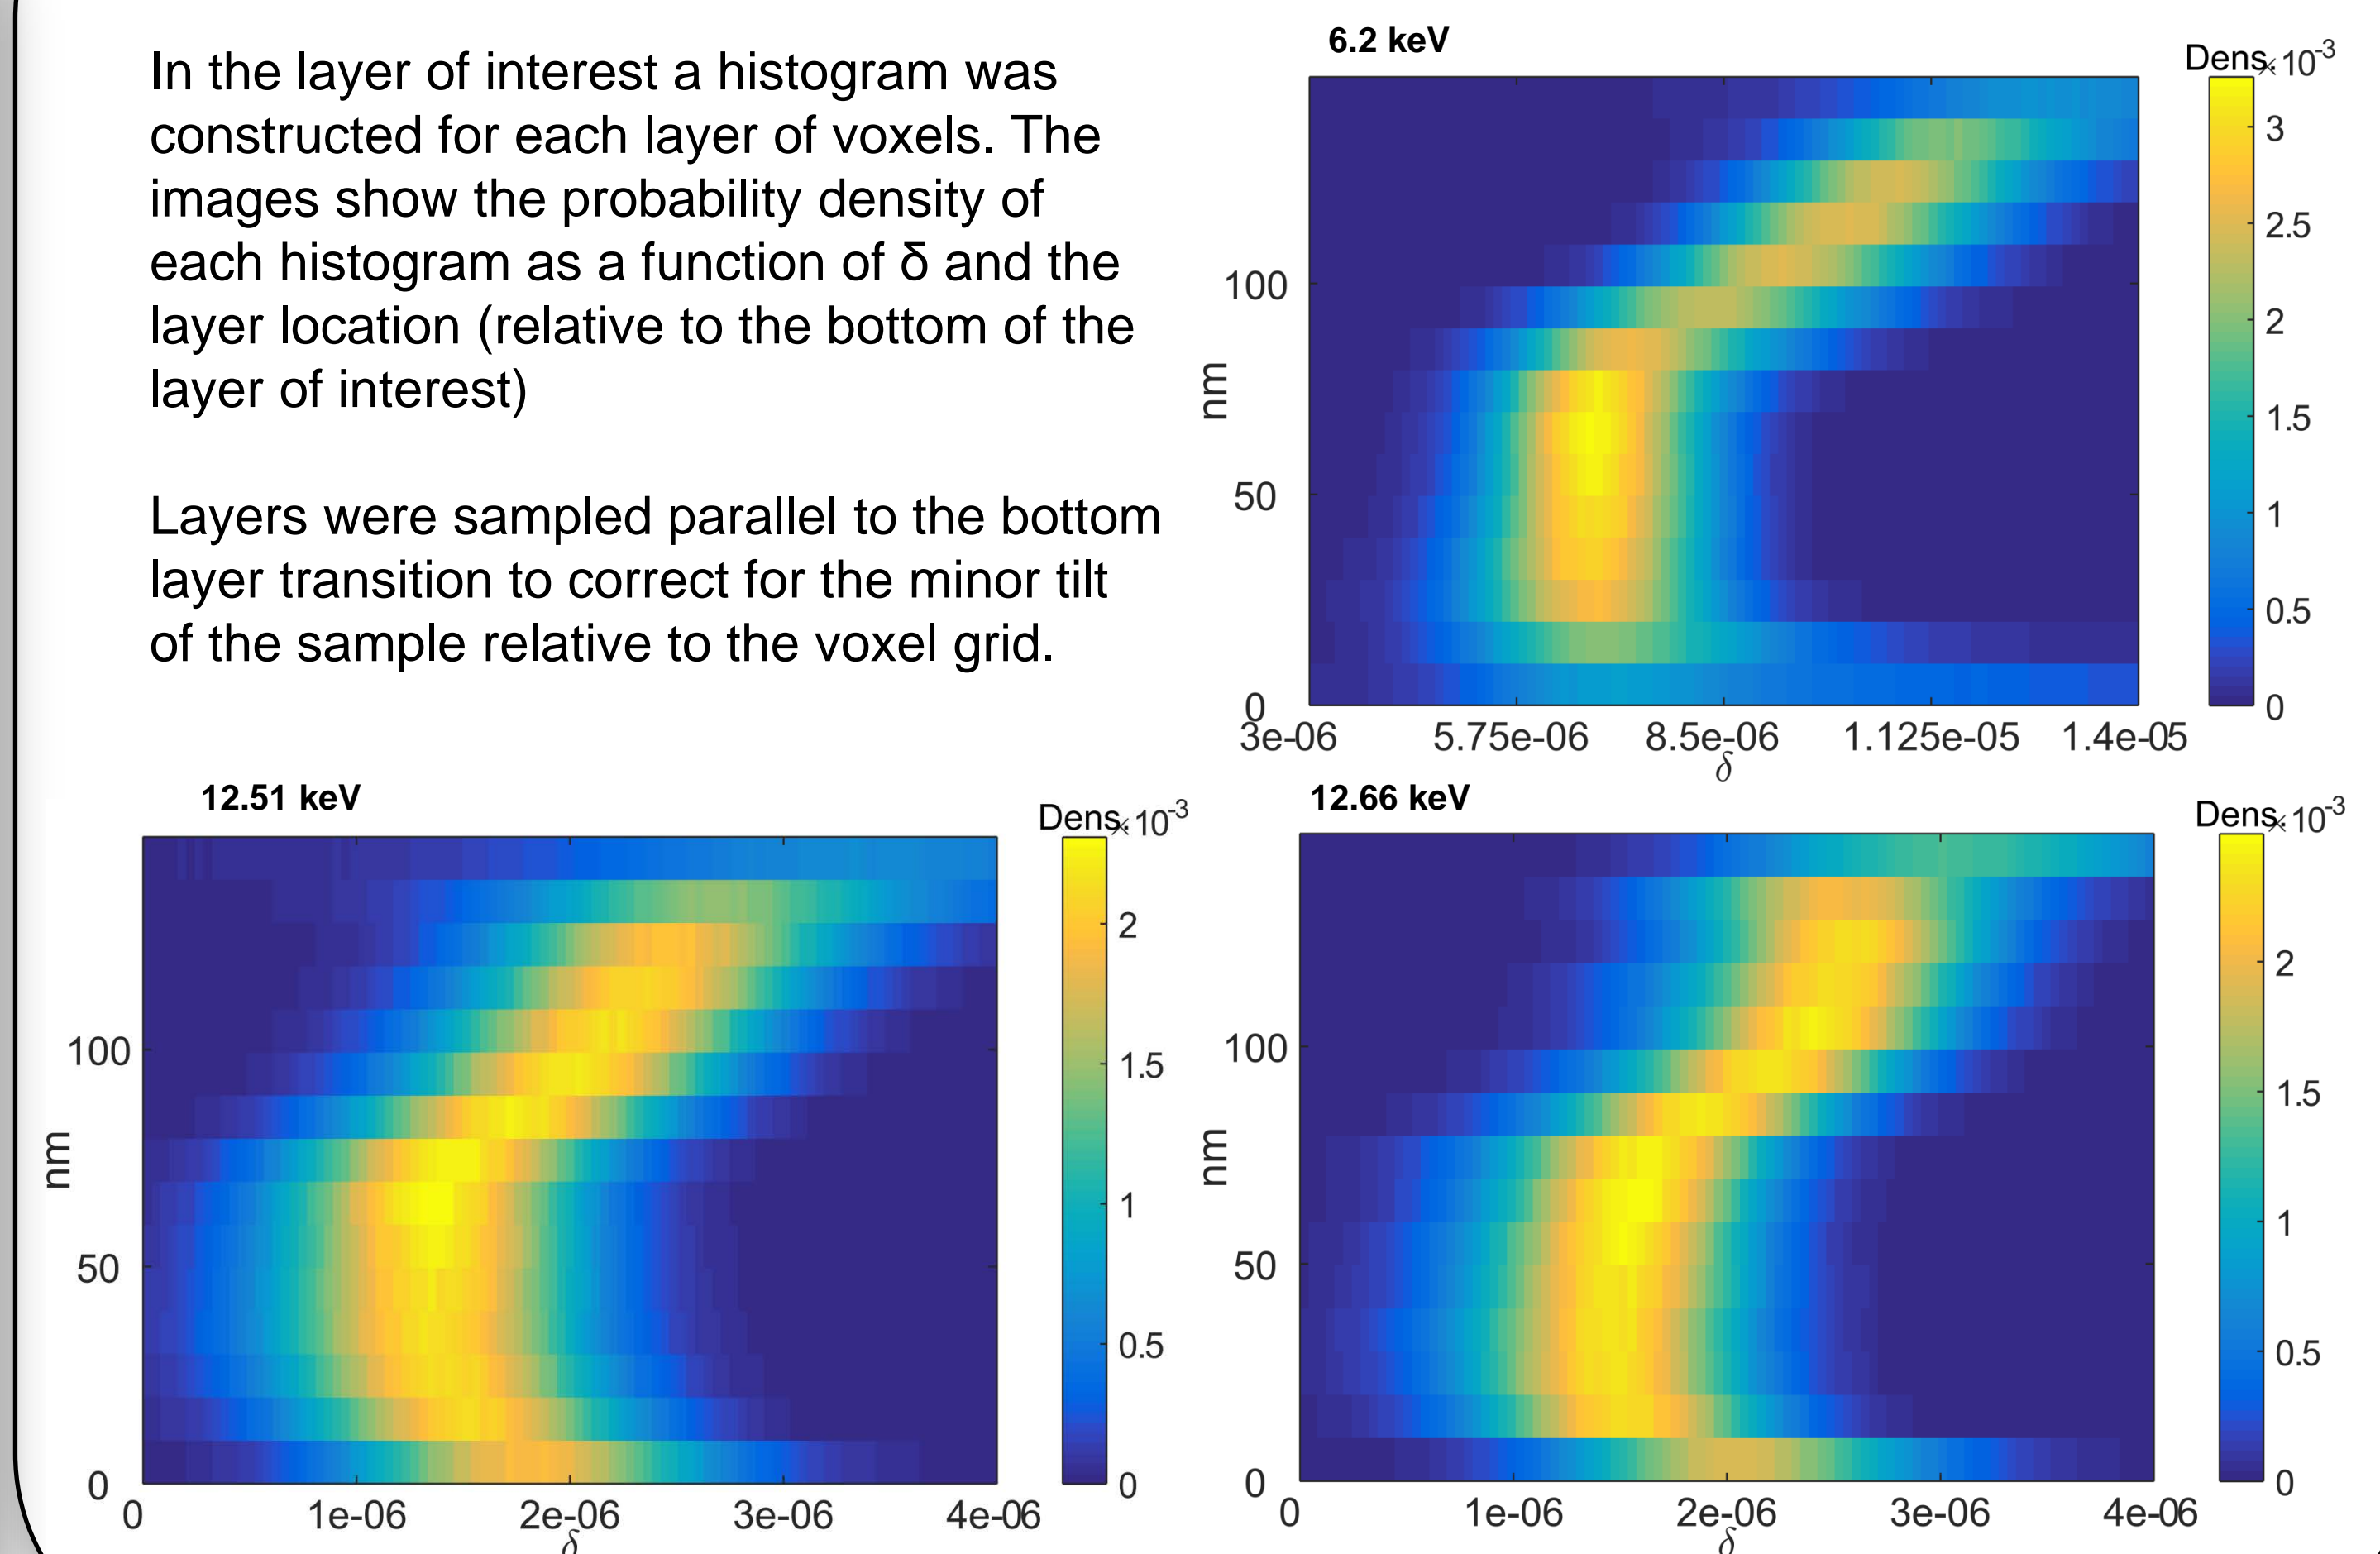


The layer of interest and its neighboring layers

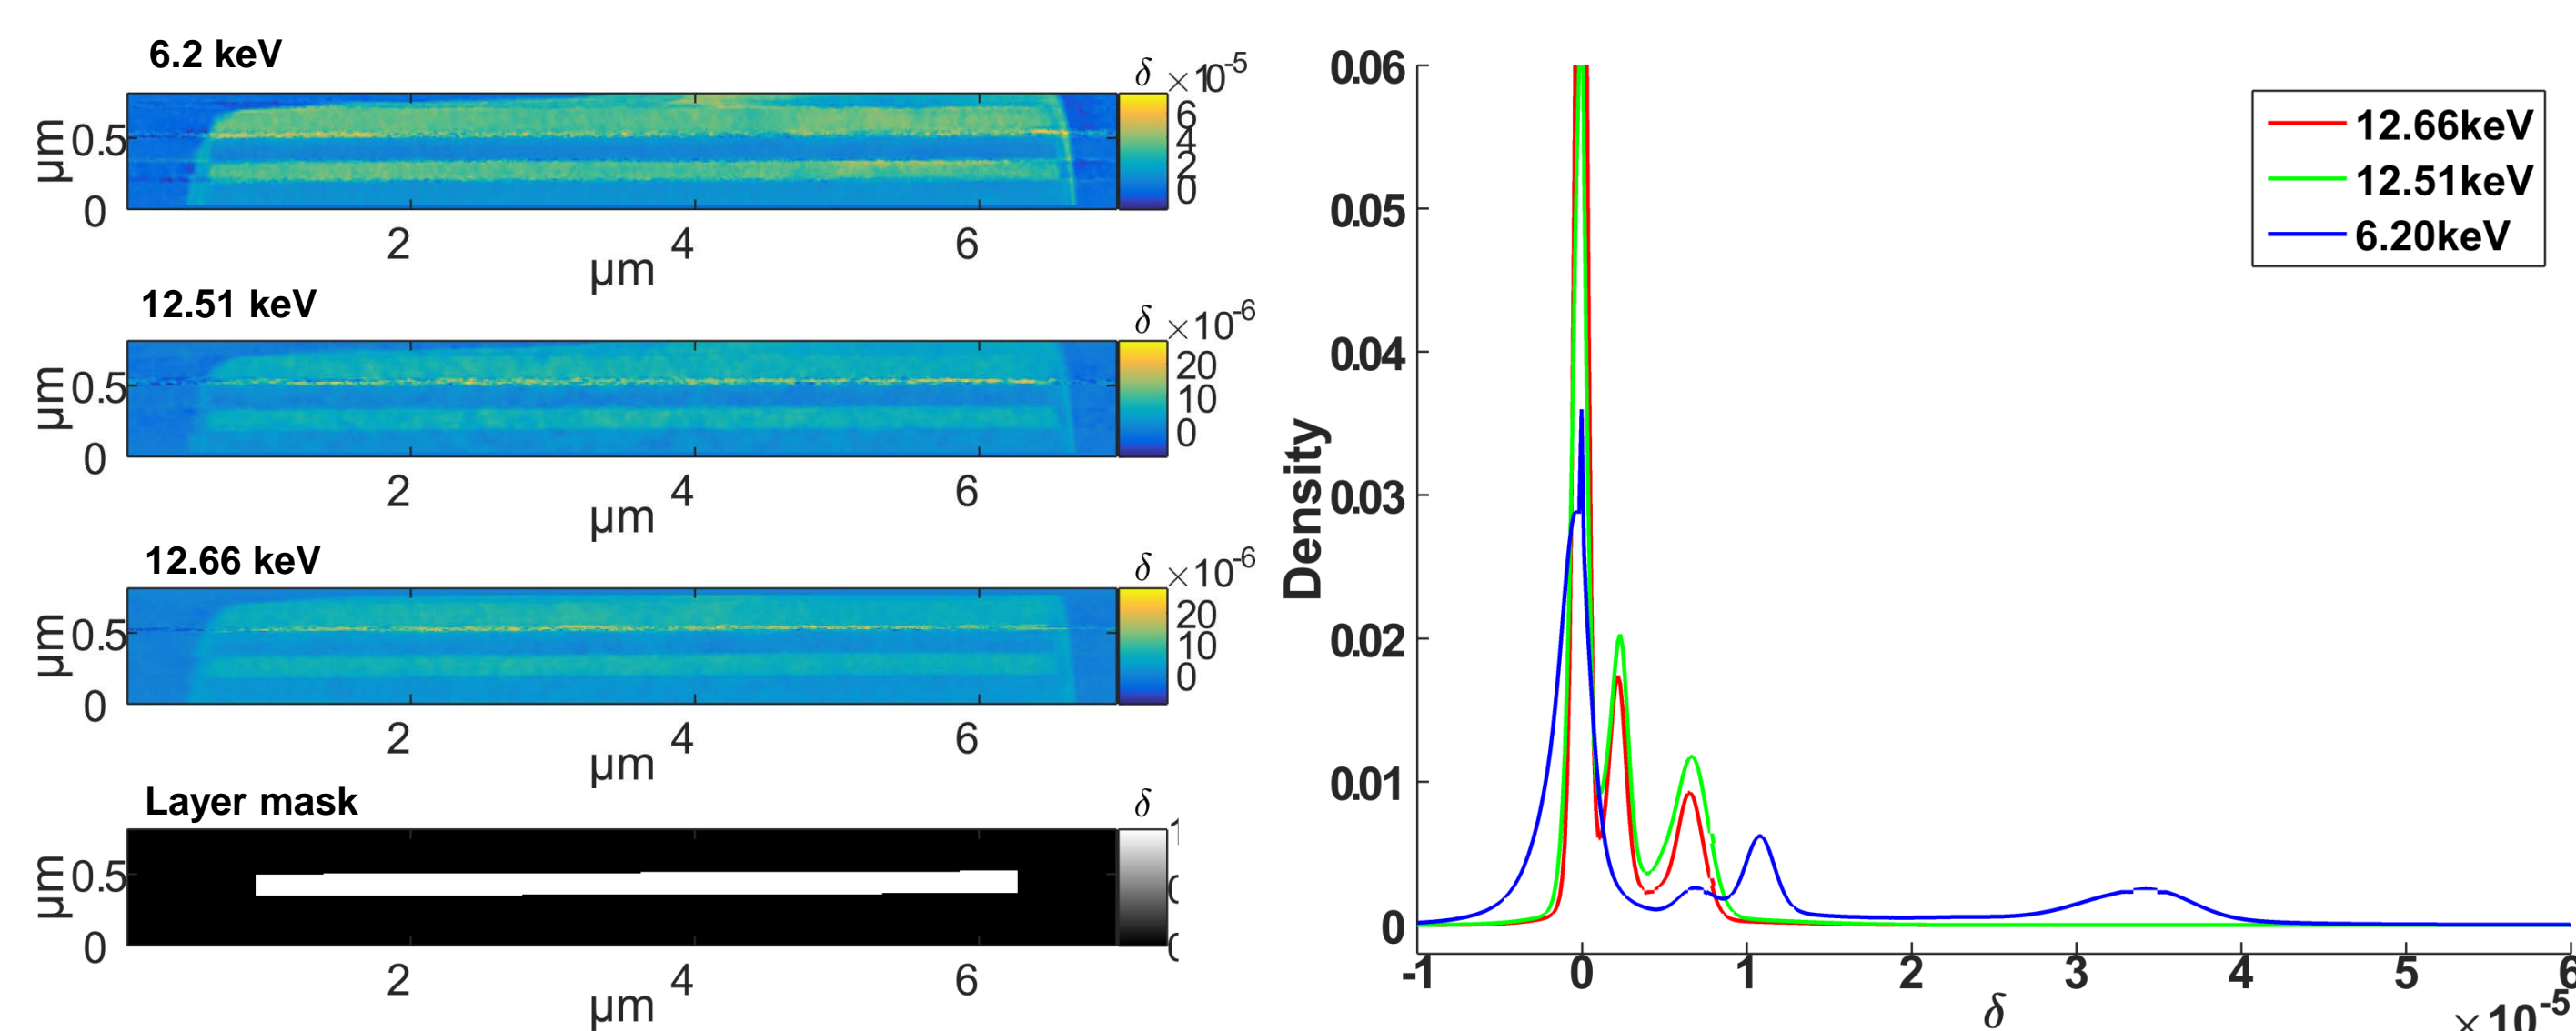


Correlation between tomograms at different energies within a voxel layer in the region of interest

For the voxel layer corresponding to 120 nm above the lower layer transition, correlation between the delta values in each pair of tomograms was tested.

The figures show the probability density of the voxel delta values for pairs of tomograms along with the corresponding correlation factors.

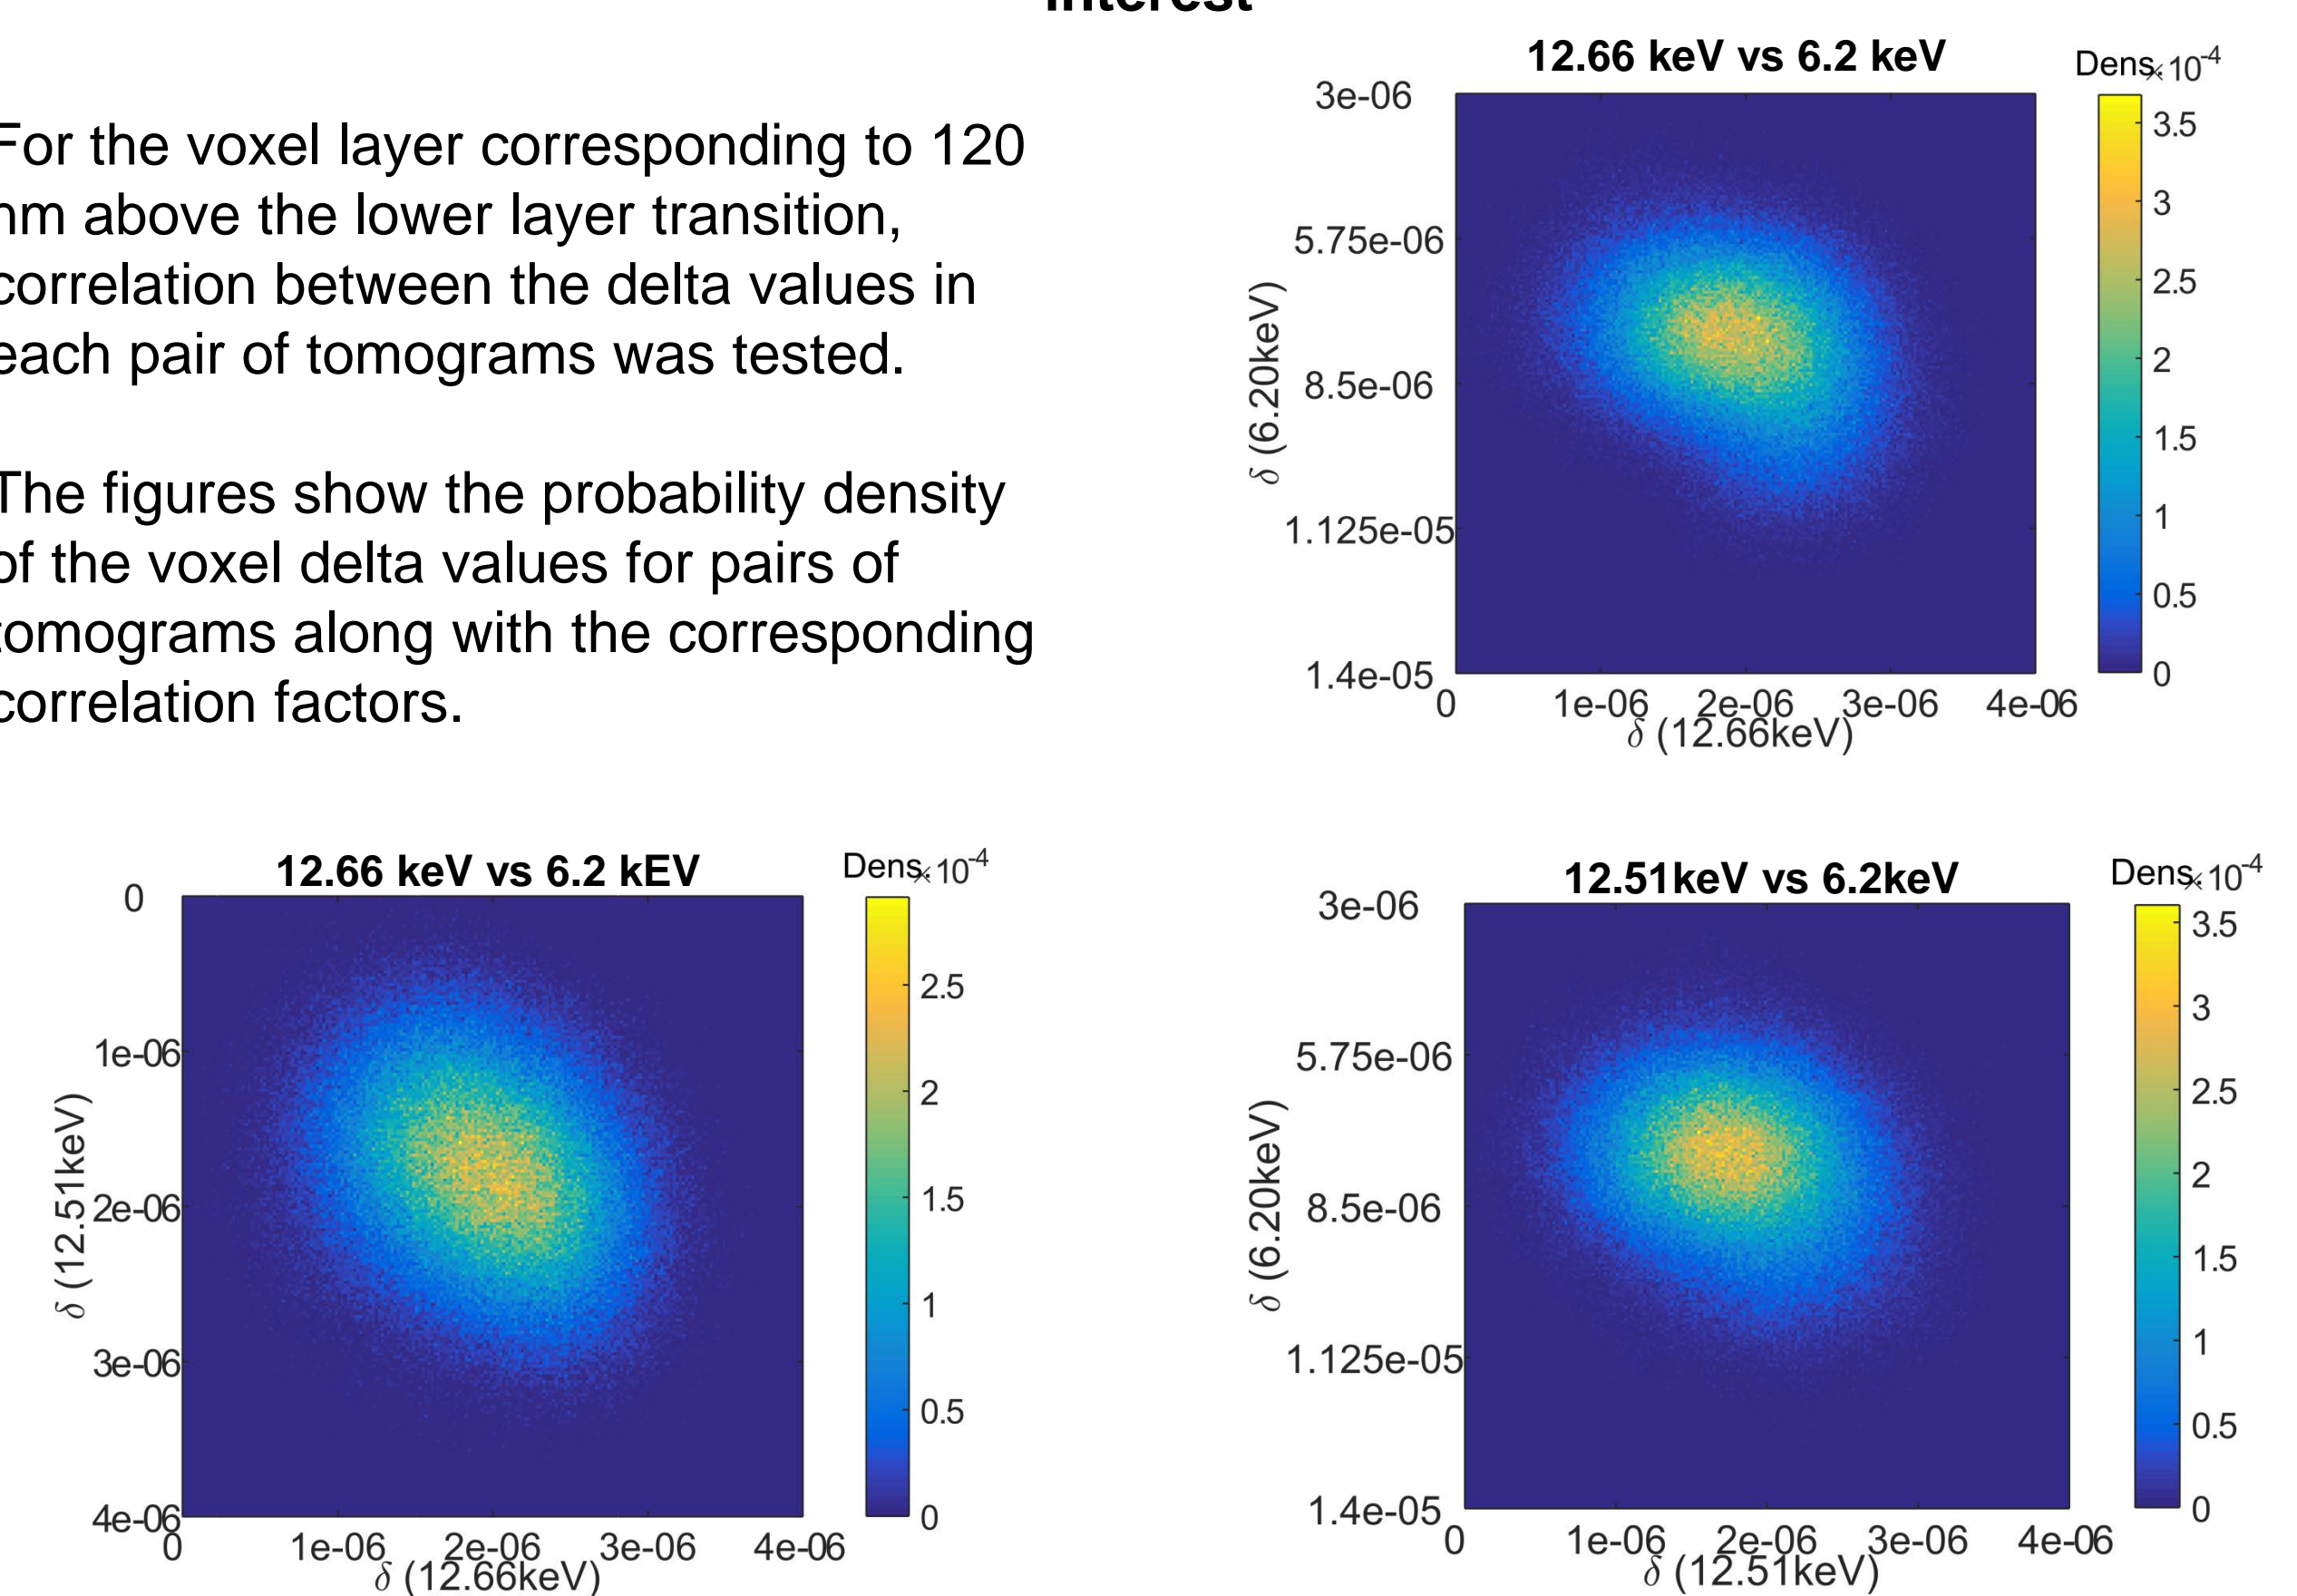

The layer of interest

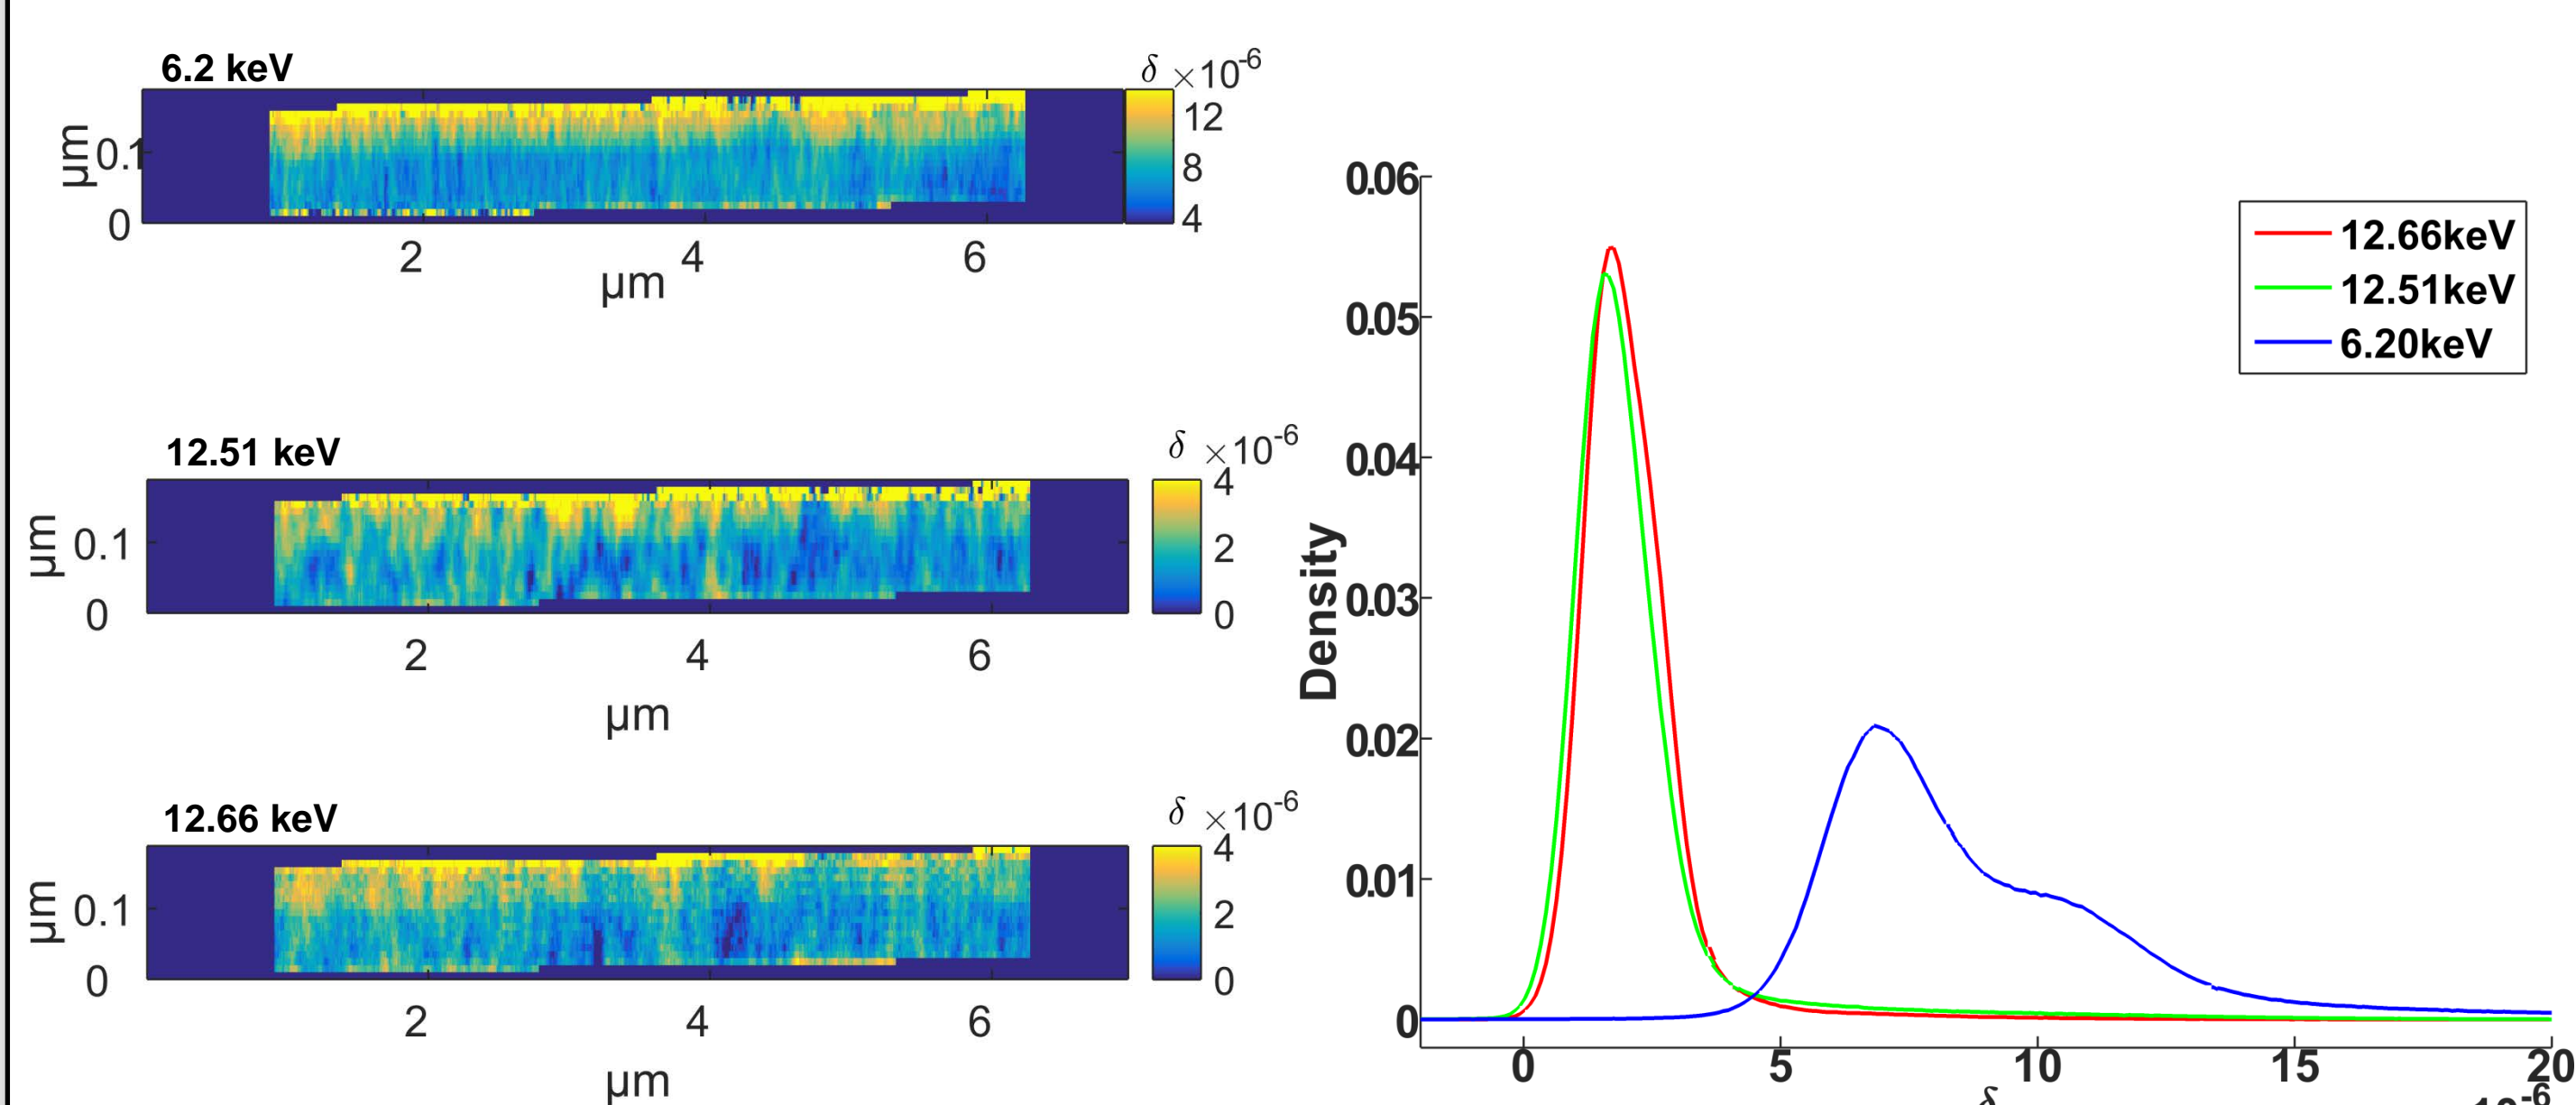

Conclusion

The analysis of the effect of imaging near the Se absorption edge is complicated by two issues: 1) The replacement of S with Se in the P3HT molecule only contributes a small amount to the overall scattering properties of the material. 2) The data shows issues of $>2\pi$ phase shifts at layer interfaces parallel to the beam resulting in artefacts and increased noise levels near the layers of interest. Combined, these two effects make the Se absorption edge challenging to utilize for resolving the internal structure of the P3HS layer for the present data.

These preliminary results are a step towards the overall goal of resolving and studying the internal structure of the absorber layer in polymer solar cells. Future work will revisit the data using new alignment and reconstruction procedures and will also incorporate the absorption in the analysis. Future tomograms will be sought acquired at an orientation where the layers are not parallel to the beam.

Acknowledgements

The authors would like to thank Manuel Guizar-Sicairos for valuable assistance at the cSAXS beamline at the Paul Scherrer Institute.